


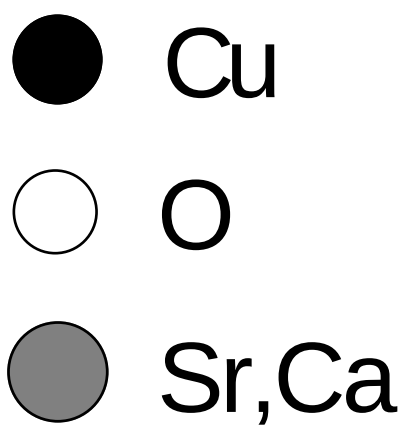
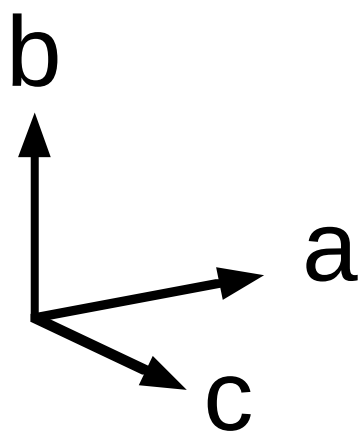


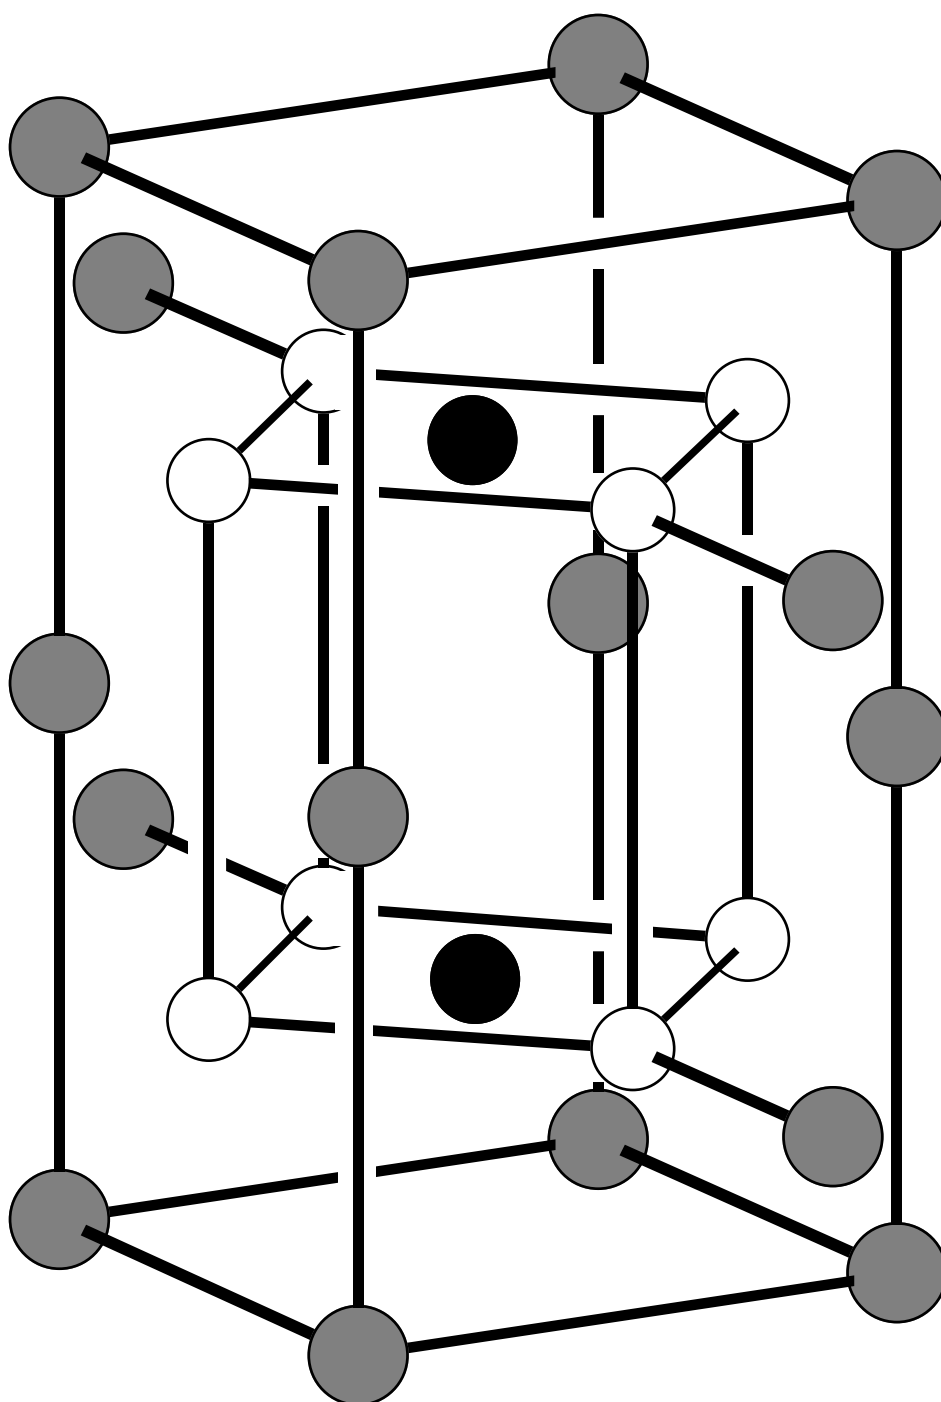

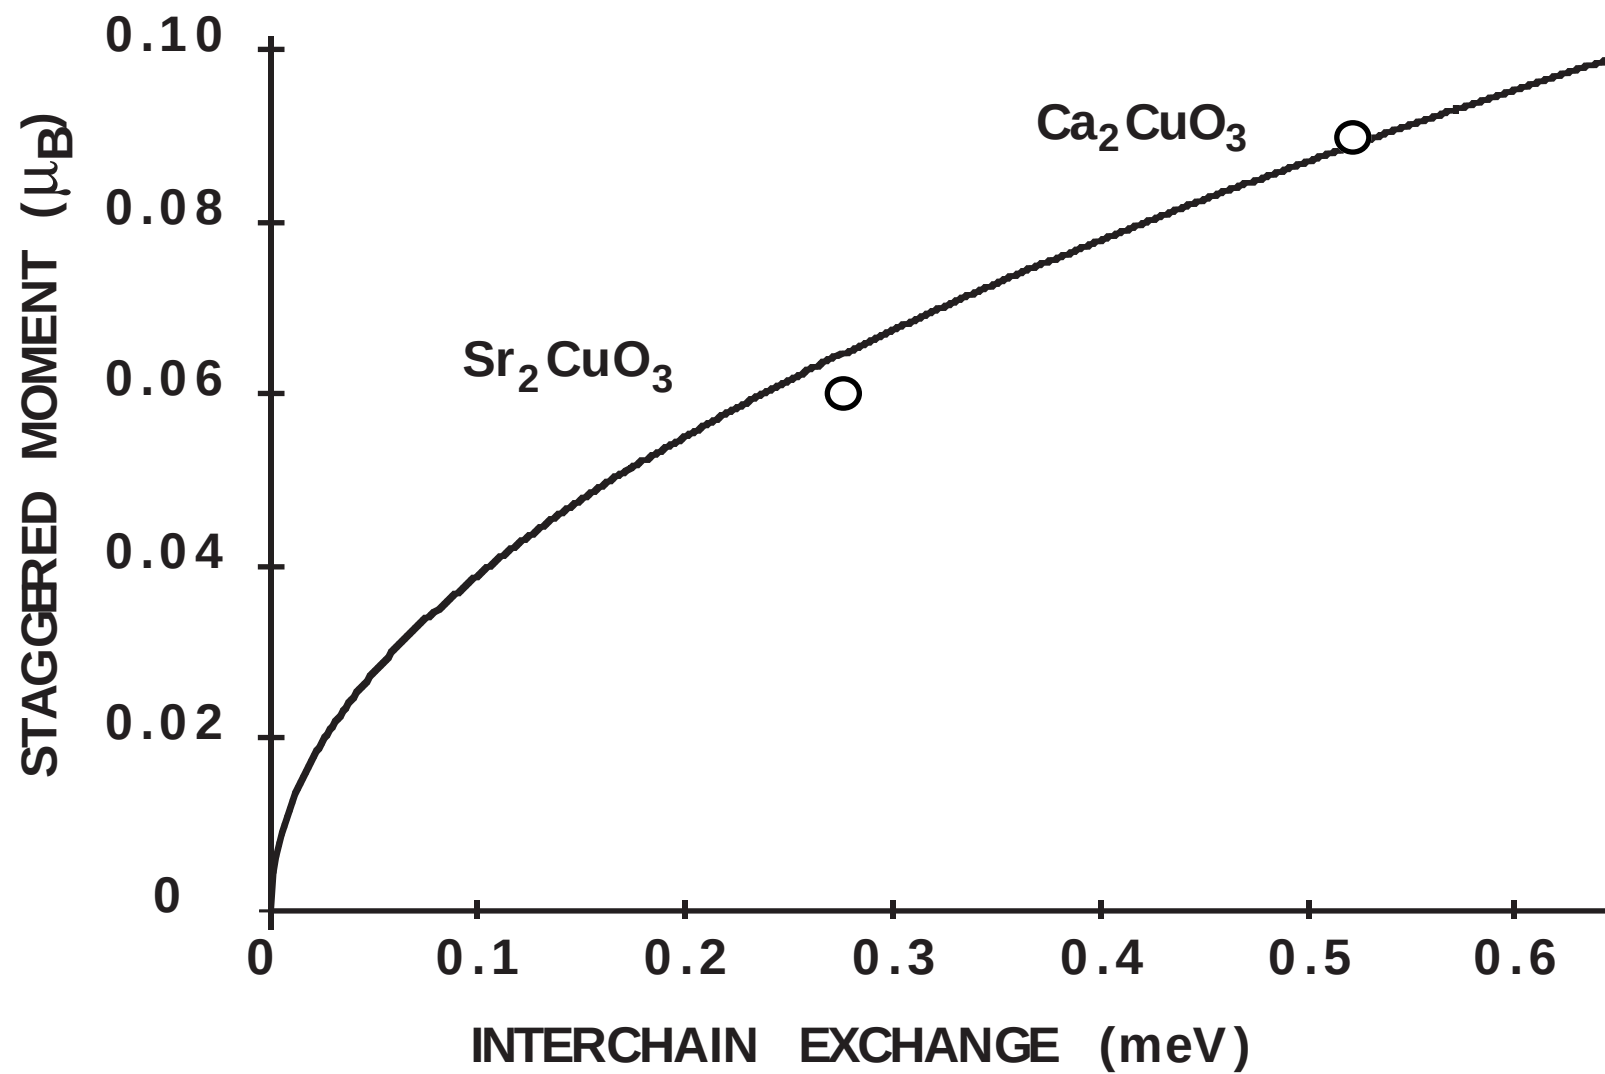

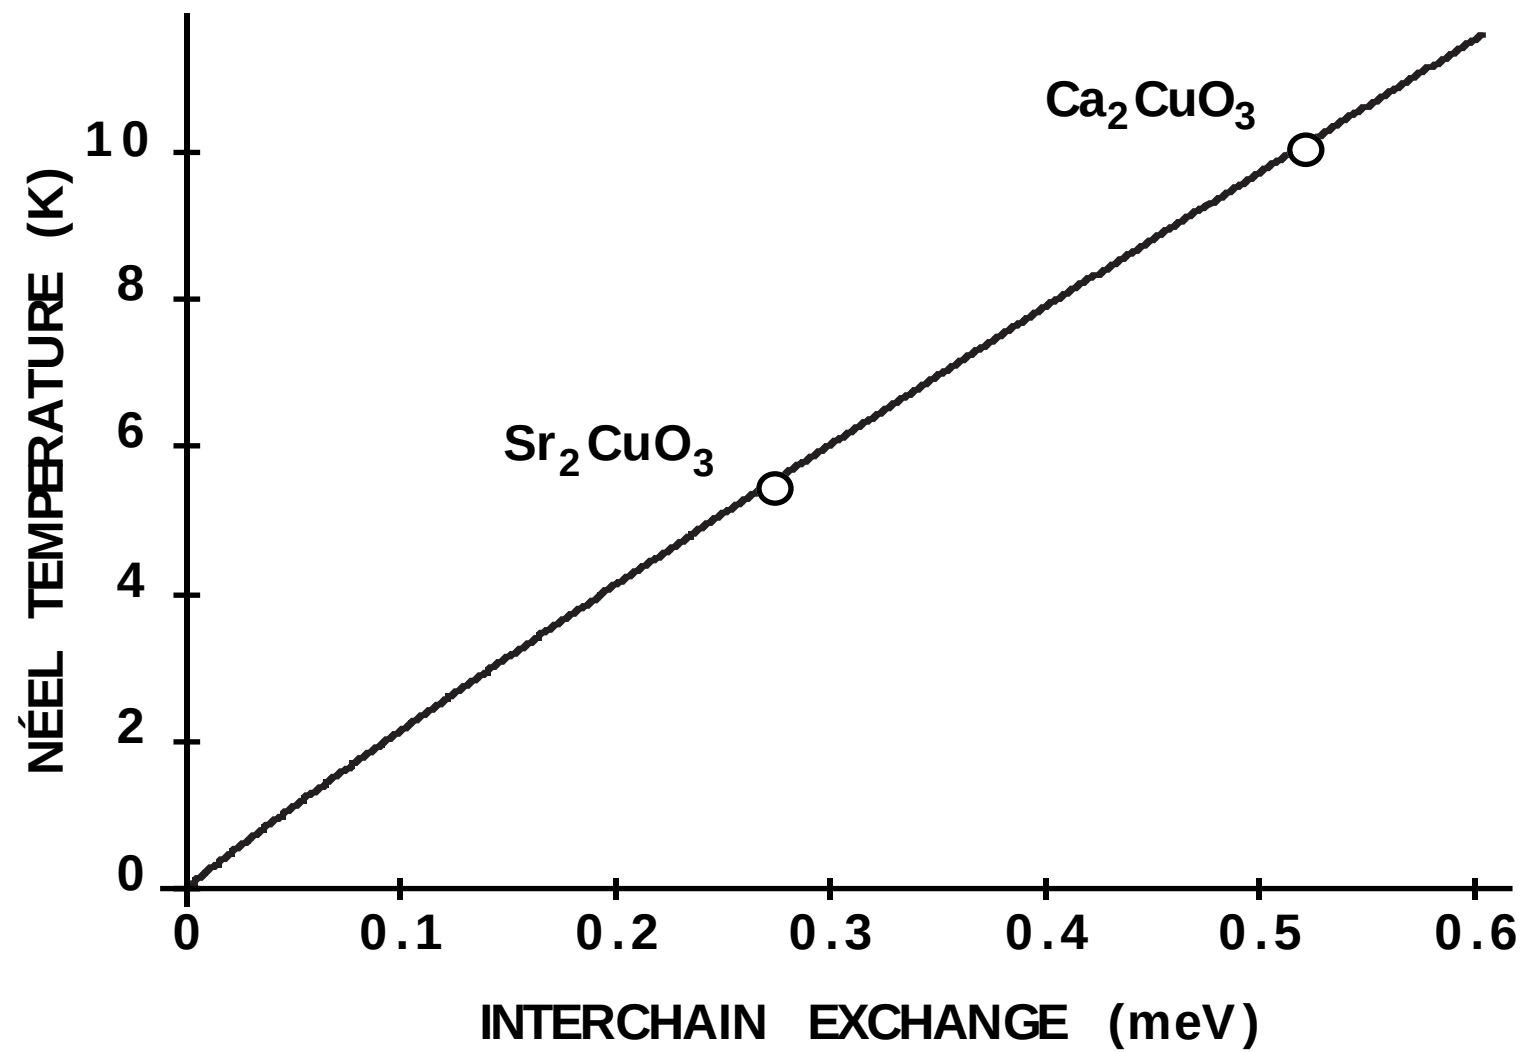

Intra- and interchain exchange in the linear cuprate antiferromagnets Ca_2CuO_3 and Sr_2CuO_3

A. B. Van Oosten

Max Planck Institut für Physik komplexer Systeme, Bayreutherstrasse 40, 01187 Dresden, Germany

Ab initio quantum chemical cluster calculations of Heisenberg exchange in linear cuprate antiferromagnets are reported. For Ca_2CuO_3 I find $J_a = -136$ meV for the intrachain coupling and $J_b = -0.52$ meV for the interchain coupling. For Sr_2CuO_3 I estimate $J_a = -136$ meV and calculate $J_b = -0.28$ meV. With these values, expressions resulting from a mean field treatment of the interchain coupling reproduce the experimental values for the staggered magnetic moment and the Néel temperature T_N surprisingly well. The linear dependence of T_N on J_b suggests that Néel order persists for any finite value of J_b .

PACS numbers: 71.10.-w, 71.27.+a, 74.25.Jb, 75.10.Jm, 75.30.Et

The one-dimensional (1D) spin 1/2 Heisenberg antiferromagnet is a nontrivial, but nonetheless integrable [1,2] quantum mechanical model with vanishing long-range magnetic order in the ground state. In real systems that contain antiferromagnetic chains there always exists interchain coupling. The linear cuprates Ca_2CuO_3 and Sr_2CuO_3 [3] presently attract much attention because they have exceptionally small ratio's of inter- to intrachain coupling, J_b/J_a , and thus are nearly ideal 1D spin 1/2 systems. This was inferred from the magnetic susceptibility and muon spin relaxation (μSR) experiments [4,5]. These materials therefore provide a unique opportunity to compare theoretical predictions with experiment, provided that the values for the coupling parameters are accurately known. Unfortunately, the values for J_a as derived from experiments vary considerably. From an analysis [6,7] of magnetic susceptibility measurements [8] a value of $-J_a \approx 135\text{-}160$ meV was found. A second susceptibility study obtained a value of

$J_a = -190$ meV [9]. An even larger value of $J = -260$ meV was estimated from the analysis of the mid-gap infrared absorption spectrum [10]. For comparison, in the planar cuprates J_a varies between -100 and -140 meV [11]. For the interchain coupling J_b no experimental value is available, but mean field expressions of the staggered magnetic moment [12,13] and the Néel temperature [12] in terms of J_b and J_a have been proposed. Recent μ SR and neutron scattering experiments [5] give precise values for the staggered moment and the Néel temperature of Ca_2CuO_3 and Sr_2CuO_3 . Clearly, accurate theoretical estimates for J_a and J_b would resolve the controversy over J_a and permit a check on the validity of the mean field approximation of the interchain coupling.

In this Letter values for J_a and J_b are computed in a manner that is entirely independent from experiment. The computational approach that can achieve this reproduces the in-plane exchange coupling in quasi-2D cuprates within experimental accuracy [11,14]. Its application to the linear cuprates and extension to the description of interchain coupling is straightforward. The approach is an accurately balanced calculation of singlet-triplet splitting of a cluster containing two Cu^{2+} ions with quantum chemical all-electron methods. Using the computed values of J_a and J_b a detailed comparison of the various theoretical predictions and experimental results is made.

The structure of $\text{Ca}(\text{Sr})_2\text{CuO}_3$ consists of two interpenetrating sublattices of infinite chains of $S=1/2$ $[\text{CuO}_3]^{-4}$ units separated by $\text{Ca}(\text{Sr})^{+2}$ ions [8,15], that are magnetically decoupled by symmetry. The magnetic behavior of a single sublattice can be described by the spin hamiltonian

$$H = - \sum_{ijk} (J_a \vec{S}_{ijk} \cdot \vec{S}_{i+1jk} + J_b \vec{S}_{ijk} \cdot \vec{S}_{ij+1k}), \quad (1)$$

where the summation runs over lattice vectors (ijk) . The chains are oriented along $\vec{a}$ and the CuO_3 -units lie in the a - c -planes, so that J_a and J_b are the intra- and interchain coupling, respectively.

The computational approach for the intrachain coupling J_a follows that of Refs. [11,14]. As a first step the (MC)SCF singlet and triplet ground states of the planar, D_{2h} symmetric, Cu_2O_7 cluster that occurs in the chains are calculated. It is necessary [11,14]

to introduce local exchange and correlation effects on the bridging oxygen atom. This is done in a second step of the calculation through admixture of excited (MC)SCF states, that differ from the MCSCF ground states by an O $\rightarrow$ Cu electron excitation. This is an example of non-orthogonal CI (NOCI) [16]. NOCI involves the computation of Hamilton and overlap matrix elements between determinants constructed from non-orthogonal orbital sets [17]. It has the advantage over conventional CI methods that it leads to a short, physically transparent wave function and that it is free of size consistency errors.

For the calculation of the interchain coupling J_b , I perform all-electron (MC)SCF calculations of the singlet and triplet ground states of D_{2h} symmetric Cu_2O_8 and $\text{Cu}_2\text{O}_8\text{M}_{16}$ (M=Ca,Sr) clusters (Fig. 1) consisting of two CuO_4 units that are translated with respect to each other by one unit vector along the b-axis, so that they are located in next-nearest neighbor chains. Since there are no ligands, the exchange originates simply from the overlap between the Cu d-orbitals and J_b can be found directly from the (MC)SCF ground state singlet-triplet splitting. For a study of the effect of the counterions, calculations were also performed on $\text{Cu}_2\text{O}_8\text{M}_{16}$ (M=Ca,Sr).

The clusters are embedded in a point charge environment that accurately represents the Coulomb potential inside the cluster region of a surrounding infinite lattice of formal ionic charges. The use of the simple point charges at nearest neighbor positions may lead to spurious occupation of diffuse orbitals [18], because these orbitals feel the strong attractive potential of the Cu^{2+} and Sr^{2+} point charges, without being repelled by the ion core [13, 16]. Therefore the potential due to the ions at the nearest neighbour positions to the cluster, is modified to be flat inside a small sphere with an ionic radius [19] around these point charges. These modified potentials improve the stability against variation of the most diffuse components of the basisset, whereas in the cluster region the potential due to the modified charges is identical to that of the bare point charges. The complete specification of the background potential is available from the authors on request.

For Cu and O the same contracted Gaussian basis sets are used as in ref. [11], namely a 14s11p6d $\rightarrow$ 8s6p3d basis set for Cu and a 9s6p $\rightarrow$ 3s3p one for O. It was found that J_b is sensitive to extension of the Cu basis with diffuse d-functions, as will be discussed

below in detail. For Ca I employed a 14s8p $\rightarrow$ 5s2p basis set of double zeta quality [20] and a 12s6p $\rightarrow$ 4s2p minimal basis set [21] and for Sr a (15s,9p,3d) $\rightarrow$ (5s,3p,1d) minimal basis set [21].

First consider the intrachain coupling. Following Ref. [11], in an SCF wavefunction for the lowest triplet state of the $[\text{Cu}_2\text{O}_7]^{-10}$ model clusters two open shell orbitals occur, denoted by d_g and d_u and transforming as a_g and b_{3u} , respectively. These orbitals can be considered even (g) and odd (u) linear combinations of Wannier-like orbitals, d_1 and d_2 , localized at the Cu. The triplet wavefunction can be written as

$$\Psi_t = | \sigma \bar{\sigma} d_g d_u | = | \sigma \bar{\sigma} d_1 d_2 | \quad (2)$$

Here σ denotes the $O(2p_\sigma)$ orbital at the bridging oxygen, which has the same symmetry as d_u . For clarity all other closed shell orbitals are suppressed in the notation. The singlet corresponding to Eq.(2) can be written as

$$\begin{aligned} \Psi_s &= (2+2S^2)^{-1/2} | \sigma \bar{\sigma} (d_1 \bar{d}_2 - \bar{d}_1 d_2) | \\ &= (2+2S^2)^{-1/2} \{ | (1+S) \sigma \bar{\sigma} d_g \bar{d}_g - (1-S) \sigma \bar{\sigma} d_u \bar{d}_u | \}, \end{aligned} \quad (3)$$

In Eq. (3) d_1 and d_2 have an overlap $S = \langle d_1 | d_2 \rangle$, which constitutes an additional variational parameter. As also found for the planar cuprates, the triplet and singlet SCF ground states are very well characterised by $\text{Cu}^{+2} (3d^9)$ and $\text{O}^{-2} (2p^6)$ and the Cu holes have almost pure $3d(x^2-y^2)$ character in a Mulliken orbital population. The singlet states (3) with optimized orbitals have $S \approx 0.04$ and their energies are 20 to 30 meV below the triplets. The wave functions (2) and (3) form an appropriate starting point of a balanced calculation of the singlet-triplet splitting [22]. At this level of the calculation the splitting corresponds to Anderson superexchange [23], which is due to charge transfer excitations of the type $d_1^1 d_2^1 \rightarrow d_1^2 d_2^0 + d_1^0 d_2^2$ that can only occur for the singlet.

As a next step I admix to Ψ_t and Ψ_s relaxed charge transfer excitations of the form $d_1^1 (\sigma)^2 d_2^1 \rightarrow d_1^1 (\sigma)^1 d_2^2 \pm d_1^2 (\sigma)^1 d_2^1$. Admixture of *unrelaxed* excitations of this type

has no effect, but this is quite different for the relaxed charge transfer excitations. As discussed in full detail in Ref. [11], the charge transfer states, of ${}^3B_{3u}$ and ${}^1A_g$ symmetry, can be written as

$$\Psi_t^* = | d_u \bar{d}_u d_g \sigma | , \quad (4)$$

$$\Psi_s^* = \frac{(1+S^*) | d_g \bar{d}_g u_1 \bar{u}_1 | - (1-S^*) | d_g \bar{d}_g u_2 \bar{u}_2 |}{\sqrt{(2+2S^{*2})}} . \quad (5)$$

In the excited singlet state Ψ_s^* (5) again an overlap between open shell orbitals is allowed, now between the $O(2p_\sigma)$ and the $Cu(3d_u)$ orbitals. Moreover, the open shell orbitals are allowed to mix because they have the same symmetry. It turns out that the orbitals u_1 and u_2 approximately correspond to bonding and antibonding combinations of d_u and σ . It should be noted that in the wave functions (2-5) the orbitals are separately optimized. An energy separation of about 10 eV between ground and excited states is found. As for the planar cuprates, $S^* \approx 0.55$ is obtained. This result can be interpreted as a tendency towards covalent bond formation between the bridging O and the remaining Cu^{2+} neighbour in the excited singlet state, which is enhanced by orbital relaxation. These effects are absent in Ψ_t^* . The Cu_2O_7 wave functions of the linear cuprates obtained here closely resemble those of the analogous clusters for the planar cuprates.

The NOCI calculation involves a 2x2 non-orthogonal diagonalization for the triplet. As argued in Ref. [11], the singlet involves a 5x5 non-orthogonal diagonalization, since S , S^* and the parameter determining u_1 and u_2 as orthogonal combinations of d_u and σ have to be reoptimized. The results are displayed in Table I. For both Ca_2CuO_3 and Sr_2CuO_3 a value of $J_a = 119$ meV is obtained, which is close to value for La_2CuO_4 reported in ref. [Van Oosten, 1996 #205]. When the 16 nearest Ca neighbors are included, as all electron atoms, the value for Ca_2CuO_3 increases to 136.5 meV. In view of the Cu_2O_7 results, it is reasonable to adopt this value also for Sr_2CuO_3 . This value agrees with previous analyses [6,7] have given of the susceptibility data [8]. Much larger values, such as $J_a = -190$ meV [9] and $J_a = -260$ meV [10] should be excluded.

Let us now turn to the calculation of the interchain exchange J_b from the singlet-triplet splitting of the $[\text{Cu}_2\text{O}_8]^{-12}$ clusters. There are no bridging O so that J_b equals the singlet-triplet splitting at the (MC)SCF level and is obtained directly from wave functions analogous to equations to (2) and (3). Note that the orbital d_u now transforms as b_{1u} and that the σ orbital can be suppressed in the notation. Since the Cu-Cu distance of 3.278 Å (Ca_2CuO_3) and 3.494 Å (Sr_2CuO_3) is rather larger than a Cu-Cu inter-atomic distance, I investigated the effect of augmenting the basis sets with diffuse Cu d- and O p-functions. The effect of extending the d-basis is substantial and saturates after addition of $\alpha=0.05$, 0.016 and 0.005 functions. An extra $\alpha=0.04$ O p-function has negligible effect. The results are listed in Table II. The diffuse functions describe the exponential decay of the d-orbital in the region of space where the overlap is generated and contribute little to the total energy. The interchain coupling saturates towards values of $J_b=0.33$ meV (Ca_2CuO_3) and $J_b=0.23$ meV (Sr_2CuO_3). The overlaps of the d-orbitals are close to 4 %. The calculation was repeated for $\text{Cu}_2\text{O}_8\text{M}_{16}$ (M=Ca,Sr) clusters that include the nearest 16 counterion neighbors, using the extended Cu basis. As seen from Table III, the effect of the counterions is a 50 % increase of $-J_b$ for Ca_2CuO_3 and 20 % increase for Sr_2CuO_3 , where it makes no difference whether the double zeta or the minimal basis set is used for Ca. These values can be inserted into expressions for the staggered moment and the Néel temperature obtained from a mean field treatment of J_b [12,13]. It should be noted that a chain couples antiferromagnetically to two out of four next-nearest neighbors, whereas the coupling to the other two (J_c) is ferromagnetic and should be considerably smaller than J_b . The coupling to the four nearest neighbors cancels in the ordered state. As can be seen from Table IV, this yields values in excellent agreement with experiment [5]. Equally good agreement exists between the measured values and the mean field prediction for T_N [12], when the calculated J_a and J_b are used. The situation is graphically displayed in Fig. 2. In view of the small number of neighbor chains, it is quite surprising that mean field theory should perform so well in the present case. The linear dependence T_N as a function of J_b at J_b/J as small as 2.4×10^{-3} supports the idea that long range magnetic order persists at arbitrarily small coupling ratio [24].

In summary, the intra- and interchain magnetic coupling, J_a and J_b , in Ca_2CuO_3 and Sr_2CuO_3 were computed. I obtain values of $J_a = -119$ meV for the intrachain coupling in both Ca_2CuO_3 and Sr_2CuO_3 , respectively, with Cu_2O_7 clusters. This value is close to the value previously obtained for La_2CuO_4 . For the $\text{Cu}_2\text{O}_7\text{M}_{16}$ ($\text{M}=\text{Ca}, \text{Sr}$) clusters J_a is enhanced to -136 meV, which agrees with several analyses of the magnetic susceptibility of Sr_2CuO_3 . For the interchain coupling I obtain $J_b = -0.52$ meV and $J_b = -0.28$ meV, respectively. With these values mean field expressions predicts magnetic moments and Néel temperatures in close agreement with experimental data. This constitutes strong support to the mean field treatment of the interchain coupling and to the idea that magnetic order occurs for any finite interchain coupling.

I am grateful to Stephan Drechsler, Walter Stephan and Karlo Penc for stimulating discussions.

Tables

	a	b	c
$\text{Sr}_2\text{CuO}_3 (\text{Cu}_2\text{O}_7)$	-32.8	-118.7	-100..-260 ¹
$\text{Ca}_2\text{CuO}_3 (\text{Cu}_2\text{O}_7)$	-36.5	-118.8	—
$\text{Ca}_2\text{CuO}_3 (\text{Cu}_2\text{O}_7\text{Ca}_{16})$	-48.1	-136.5	—

Table I. Calculated intrachain coupling J_a of the linear cuprates Sr_2CuO_3 and Ca_2CuO_3 :

a) Triplet-singlet splitting of Eqs. (2,3); b) Non-orthogonal CI involving (2,3) and (4,5);
d) Experiment. ¹Refs. [6-10].

added diffuse exponent		J_b (meV)	
O 2p	Cu 3d	Sr_2CuO_3	Ca_2CuO_3
—	—	-0.167	-0.209
—	0.05	-0.176	-0.252
—	0.05, 0.016	-0.226	-0.321
—	0.05, 0.016, 0.005	-0.228	-0.330
0.04	—	-0.166	-0.213

Table II. Calculated interchain coupling J_b of Sr_2CuO_3 and Ca_2CuO_3 from Cu_2O_8 clusters, for various basis sets.

cluster	J_b (meV)	
	Cu_2O_8	$\text{Cu}_2\text{O}_8\text{M}_{16}$
Sr_2CuO_3	-0.228	-0.276
Ca_2CuO_3	-0.330	-0.522

Table III. Calculated interchain coupling J_b of Sr_2CuO_3 and Ca_2CuO_3 for Cu_2O_8 and $\text{Cu}_2\text{O}_8\text{M}_{16}$ (M=Sr,Ca) clusters.

	magnetic moment (μ_B)		Néel temperature (K)	
	Mean field ^{1,2}	μSR ³	Mean field ²	μSR n-diffraction ³
Sr_2CuO_3	0.065	0.06(1)	5.58	5.41(1)
Ca_2CuO_3	0.089	0.09(1)	10.12	10

Table IV. Mean field and experimental staggered magnetic moment and Néel temperature in Sr_2CuO_3 and Ca_2CuO_3 , using $\text{Cu}_2\text{O}_8\text{M}_{16}$ (M=Sr,Ca) clusters. ¹Ref. [13]. ²Ref. [12]. ³Ref. [5].

Figure captions

FIG. 1. The $\text{Cu}_2\text{O}_8\text{M}_{16}$ ($\text{M}=\text{Sr}, \text{Ca}$) cluster.

FIG. 2. Staggered magnetic moment versus interchain coupling $|\text{J}_b|$. The solid curve represents the mean field expression. The points correspond to Table IV.

FIG. 3. Néel temperature versus the interchain coupling $|\text{J}_b|$. The solid curve represents the mean field expression. The points correspond to Table IV.

- [1] H.A. Bethe, Z. Phys. **71** (1931) 205.
- [2] R. Ohrbach, Phys. Rev. **112** (1958) 309.
- [3] C.L. Teske and H. Müller-Buschbaum, Z. Anorg. Allg. Chem. **371** (1969) 325; *ibid.* **379** (1970) 234.
- [4] A. Keren et al., Phys. Rev. B **48** (1993) 12926.
- [5] K.M. Kojima et al., Phys. Rev. Lett. **78** (1997) 1787.
- [6] S. Eggert, Phys. Rev. B **53** (1996) 5116.
- [7] S.-L. Drechsler et al., Phys. Rev. B **53** (1996) 11328.
- [8] T. Ami et al., Phys. Rev. B **51** (1995) 5994.
- [9] N. Motoyama, H. Eisaki and S. Uchida, Phys. Rev. Lett. **76** (1996) 3212.
- [10] H. Suuzura et al., Phys. Rev. Lett. **76** (1996) 2579.
- [11] A.B. Van Oosten, R. Broer and W.C. Nieuwpoort, Chem. Phys. Lett. **257** (1996) 207.
- [12] H.J. Schulz, Phys. Rev. Lett. **77** (1996) 2790.
- [13] Z. Wang, Phys. Rev. Lett. **78** (1997) 126.
- [14] A.B. Van Oosten, R. Broer and W.C. Nieuwpoort, Int. J. Quant. Chem. **QCS29** (1995) 241.
- [15] M. Hjorth and J. Hyldtoft, Acta Chem. Scand. **44** (1990) 516.
- [16] R. Broer and W.C. Nieuwpoort, Theor. Chim. Acta **73** (1988) 405.
- [17] The program GNOME was written for this purpose by R. Broer, J. Th. van Montfort and B. Vunderink.
- [18] R.L. Martin, J. Chem. Phys. **98** (1993) 8691.
- [19] R.D. Shannon, Acta Crystallogr. A **32** (1976) 751.
- [20] A. Schafer, H. Horn and R. Ahlrichs, J. Chem. Phys. **97** (1992) 2571.
- [21] R. Poirier, R. Kari and I.G. Csizmadia, in "Handbook of gaussian basis sets" (Elsevier, Amsterdam, 1985).
- [22] R. Broer and W.J.A. Maaskant, Chem. Phys. **102** (1986) 103.
- [23] P.W. Anderson, Phys. Rev. **115** (1959) 2.
- [24] I. Affleck, M.P. Gelfand and R.P. Singh, J. Phys. A: Math. Gen. **27** (1994) 7313.